

## Adsorption Kinetic of 8-Hydroxyquinoline on Malachite

Gabriela OPREA, Angela MICHNEA and Cristina MIHALI  
North University of Baia Mare, Romania  
76 Victoriei Street, code 430122

**Abstract:** Influence of temperature and collector concentration on its adsorption rate on mineral surface was studied as regarding to the 8-hydroxyquinoline/malachite system. Theoretical equations as well as experimental data may be useful to estimate the adsorption rate and kinetics connected to the conditioning stage in mineral flotation in order to optimise the selectivity and the recovery of the desired mineral.

**Key words:** Flotation, adsorption density, reaction rate constants, isotherms, oxine, equilibrium

### INTRODUCTION

Reagents with chelating action are used in the analytical chemistry due to their selectivity for certain metallic ions in solution<sup>[1]</sup>. The functional groups of the reagent are forming stable chelated compounds with the specific metallic ions. These reagents are used for ores containing oxide minerals when neither good recovery with classic collectors, nor selective separation of tailings minerals is achieved<sup>[2,3]</sup>.

Among these reagents, 8-hydroxyquinoline (oxine) which is successfully used in the analytical chemistry forms stable chelating complexes with many metal cations. It has been reported in mineral processing, that oxinates act as collectors through chemisorption on mineral particle surfaces during the flotation process<sup>[4,5,6]</sup>. Based on the fact that malachite contains the Cu(II) ion and 8-hydroxyquinoline forms in solution stable chelating compounds with this ion, it is possible to recover copper from malachite by flotation with this chelating agents acting as collector<sup>[7,8]</sup>.

The theoretical approaches of phenomena occurring during the flotation process are studied in many papers. The occurrence of chemical bonds between the chemisorped species and the mineral surface is proved by the similitude of IR spectra of bulk Cu oxinate and of the superficial compound resulted when malachite surface was treated with oxine solution<sup>[9]</sup>. It is well recognized already that the adsorption reaction of the collector on the mineral surface is the most important factor affecting the floatability of valuable minerals.

In this paper theoretical estimations and experimental tests were performed in order to study the

kinetic of the adsorption of 8-hydroxyquinoline on malachite.

### MATERIALS AND METHODS

Solutions of 8-hydroxyquinoline in 10% acetic acid with concentration between  $4 \cdot 10^{-5}$  mol L<sup>-1</sup> and  $50 \cdot 10^{-5}$  mol L<sup>-1</sup> were used in the experiments. Pure malachite, selected from Altan Tepe ore, Romania, was dry crushed by hand and sieved to get the particle size fraction of 40 – 80 µm.

In order to study the adsorption kinetic, 1 g of mineral was suspended in 100 mL solution in closed bottles and pH 8 was maintained by adding alkaline solution. The suspension was continuously gently shaken using the IKA HS 260 basic shaker.

Measurements of the oxine concentration at different time periods were performed by UV-VIS molecular absorption spectrometry at 319 nm wavelengths. Before starting the experiments, the adsorption spectra of the 8-hydroxyquinoline in 10% acetic acid solution were scanned from 200 to 400 nm in order to detect the wavelength of the adsorption peak. We used an UV-VIS CECIL 8000 spectrometer with 1 cm deep quartz cells.

The influence of the initial concentration of the reagent on the adsorption kinetic at constant temperature of 25°C was studied. The following initial concentrations of oxine were used:  $4 \cdot 10^{-5}$  mol L<sup>-1</sup>,  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> and  $50 \cdot 10^{-5}$  mol L<sup>-1</sup>. During each test, solution sampling was performed each 0,5 minute within the first 9 minutes, then each 2 or 3 minutes, until the residual concentration of oxine in solution remains constant (within maximum 26 minutes).

Keeping constant the initial  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> oxine concentration and increasing the temperatures,

**Corresponding Author:** Angela MICHNEA, North University of Baia Mare, Romania 76 Victoriei Street, code 430122

from 25°C, to 35°C and thereafter to 45°C, other series of experiments were carried out. The residual oxine concentration was determined in each case at the same time periods, till the concentration remains constant.

## RESULTS AND DISCUSSIONS

**Influence of the initial oxine concentration on the adsorption kinetic of oxine on malachite:** The experimental data obtained for all the initial oxine concentrations ( $4 \cdot 10^{-5}$  mol L<sup>-1</sup>,  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> and  $50 \cdot 10^{-5}$  mol L<sup>-1</sup>) are presented in Table 1.

The adsorption density (D) of 8-hydroxyquinoline on the 40-80 μm size fraction of malachite was calculated based on the relation (1):

$$D = \frac{(c_0 - c_t)V}{1000 \cdot m} \quad (1)$$

where:

- V = the volume of the oxine solution (100 mL)
- m = mass of the malachite used in the experiment (1 g)
- c<sub>0</sub> = the initial oxine concentration, mol L<sup>-1</sup>
- c<sub>t</sub> = the oxine concentration after t minutes of adsorption, mol L<sup>-1</sup>, when equilibrium is supposed to be reached,

The available collector in solution until reaching the equilibrium (expressed as  $c_t - c_{rez, \infty}$ , where  $c_{rez, \infty}$  is the oxine concentration when adsorption equilibrium was reached and the residual concentration become constant), was also calculated.

The oxine adsorption isotherms on malachite were illustrated in Fig.1, for all the studied initial oxine concentrations at 25°C.

It may be noticed that the equilibrium is rapidly reached at low initial concentration. Thus, for the initial  $4 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration, the equilibrium adsorption density of  $0.36 \cdot 10^{-5}$  mol g<sup>-1</sup> was reached in 8 minutes; for the initial  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration, the equilibrium adsorption density of  $2.4 \cdot 10^{-5}$  mol g<sup>-1</sup> was reached in 10 minutes and respectively, for the initial  $50 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration, the equilibrium adsorption density of  $4.76 \cdot 10^{-5}$  mol g<sup>-1</sup> was reached in 12 minutes.

The shape of the adsorption density curve as a function of time is similar for all the initial concentrations; it increases logarithmically in time and tends to the equilibrium value.

It is possible to apply the first order kinetic equation for the adsorption reaction<sup>[8,10]</sup>:

$$-\frac{dc}{dt} = k(c_t - c_{rez, \infty}) \quad (2)$$

$$\ln(c_t - c_{rez, \infty}) = -k \cdot t + \text{constant } t \quad (3)$$

The variation of the oxine concentration (c<sub>t</sub>) as a function of time depends on the initial concentration (c<sub>0</sub>);  $c_{rez, \infty}$  remains constant after 8, 10 and 12 minutes, depending on the c<sub>0</sub> value.

In order to find the reaction rate constant k, we used the equation (3) and we plotted  $\ln(c_t - c_{rez, \infty})$  as a function of time for each of the studied initial oxine concentration (Fig. 2). The reaction rate constants were calculated from the straight lines slopes by statistic program. Table 2 presents the reaction rate constants and the correlation coefficients (R<sup>2</sup>) resulted from the statistic data analysis of the experimental values.

Values for k<sub>1</sub> were calculated related to all the points plotted in Fig. 2 for each initial concentration, respectively for the time period from 0 to 7.5 minutes for the initial  $4 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration; 0 to 9 minutes for the initial  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration; and 0 to 10 minutes for the initial  $50 \cdot 10^{-5}$  mol L<sup>-1</sup> concentration.

When calculating k<sub>2</sub>, the first three points in each curve were rejected; in this case  $\ln(c_t - c_{rez, \infty})$  is constant; thus only data obtained 1 minute after the test started were used. Correlation coefficients are better for k<sub>2</sub> and Fig. 2 demonstrates good linear relationships with negative slope for each group of points. The adsorption rate increases by increasing the initial concentration from  $4 \cdot 10^{-5}$  mol L<sup>-1</sup> to  $30 \cdot 10^{-5}$  mol L<sup>-1</sup> and decreases by the furthermore increasing the initial concentration to  $50 \cdot 10^{-5}$  mol L<sup>-1</sup>.

The constant increasing increment with 7% for k<sub>2</sub> related to k<sub>1</sub> for each of the initial concentration highlights that the adsorption mechanism does not depend on the initial concentration.

**Temperature influence on the adsorption kinetic of oxine on malachite:** Other tests were carried out at different temperatures as 25°C, 35°C and 45°C with solutions of oxine having the same initial  $30 \cdot 10^{-5}$  mol.L<sup>-1</sup> concentration; experimental data are presented in Table 3.

Adsorption densities (D) of 8-hydroxyquinoline on malachite of 40 – 80 μm in size were calculated with relation (1).

Figure 3 represents the influence of the temperature on the oxine adsorption on malachite. The increase of the adsorption density by increasing the temperature is obvious. Thus, equilibrium adsorption density increases from  $2.4 \cdot 10^{-5}$  mol g<sup>-1</sup> (at 25°C) to  $2.54 \cdot 10^{-5}$  mol g<sup>-1</sup> (at 35°C) and to  $2.8 \cdot 10^{-5}$  mol g<sup>-1</sup> (at 45°C), for the studied oxine initial concentration. It may be noticed that the effect of the temperature on the adsorption kinetic of oxine on malachite is not so significant.

The equilibrium is as faster reached, as the temperature is higher, respectively within 7.5 minutes at 45°C; within 8.5 minutes at 35°C and within 10 minutes at 25°C.

Table 1: Variation of oxine concentration ( $c_t$ ) as a function of time during the adsorption on malachite at different initial oxine concentrations ( $c_0$ ) at 25°C

time (minutes)	$c_0 = 4 \cdot 10^{-5}$ (mol L <sup>-1</sup> )		$c_0 = 30 \cdot 10^{-5}$ (mol L <sup>-1</sup> )		$c_0 = 50 \cdot 10^{-5}$ (mol L <sup>-1</sup> )	
	$c_t$ 10 <sup>-5</sup> mol L <sup>-1</sup>	$c_t - c_{rez, \infty}^*$ 10 <sup>-5</sup> mol L <sup>-1</sup>	$c_t$ 10 <sup>-5</sup> mol L <sup>-1</sup>	$c_t - c_{rez, \infty}^*$ 10 <sup>-5</sup> mol L <sup>-1</sup>	$c_t$ 10 <sup>-5</sup> mol L <sup>-1</sup>	$c_t - c_{rez, \infty}^*$ 10 <sup>-5</sup> mol L <sup>-1</sup>
0	4.00	3.60	30.00	24.00	50.0	47.6
0.50	4.00	3.60	29.80	23.80	49.2	46.8
0.75	3.80	3.40	28.50	22.50	47.0	44.6
1.00	3.70	3.30	26.00	20.00	44.0	41.6
1.50	3.36	2.96	22.00	16.00	39.0	36.6
2.00	2.40	2.00	18.00	12.00	32.4	30.0
3.00	1.60	1.20	12.40	6.40	20.2	17.8
3.50	1.24	0.80	10.40	4.40	17.2	14.8
4.00	1.08	0.68	9.20	3.20	14.0	11.6
4.50	1.00	0.60	8.40	2.40	11.0	8.6
5.00	0.80	0.40	8.00	2.00	8.0	5.6
5.50	0.68	0.28	7.40	1.40	6.8	4.4
6.00	0.60	0.20	7.00	1.00	6.0	3.6
6.50	0.56	0.16	6.60	0.60	4.9	2.5
7.00	0.52	0.12	6.50	0.40	4.4	2.0
7.50	0.50	0.10	6.40	0.30	3.6	1.2
8.00	0.40	-	6.20	0.20	3.2	0.8
8.50	0.40	-	6.15	0.15	3.0	0.6
9.00	0.40	-	6.10	0.10	2.8	0.4
10.0	0.40	-	6.00	-	2.6	0.2
12.0	0.40	-	6.00	-	2.4	-
.....	.....	-	.....	-	-	-
26.0	0.40	-	6.00	-	2.4	-

\* $c_{rez, \infty}$  – the oxine concentration when adsorption equilibrium was reached and the residual concentration become constant

Table 2: Reaction rate constants and correlation coefficients ( $R^2$ ) for oxine adsorption on malachite at different initial concentrations ( $c_0$ ) and 25°C

$c_0$ (mol L <sup>-1</sup> )	$k_1^*$ (min <sup>-1</sup> )	$R^2$	$k_2^{**}$ (min <sup>-1</sup> )	$R^2$
$4 \cdot 10^{-5}$	0.5227	0.9878	0.5621	0.9962
$30 \cdot 10^{-5}$	0.6356	0.9916	0.6685	0.9960
$50 \cdot 10^{-5}$	0.5547	0.9789	0.5953	0.9855

\*  $k_1$  was statistically calculated related to all the points plotted in Fig. 4, \*\* $k_2$  was calculated with data obtained 1 minute after the test started

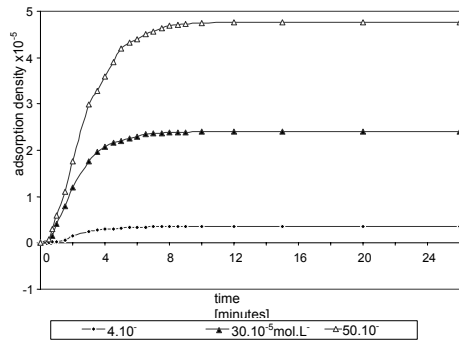


Fig. 1: Variation of the adsorption density of oxine on malachite as a function of time at 25°C for all the studied initial oxine concentrations

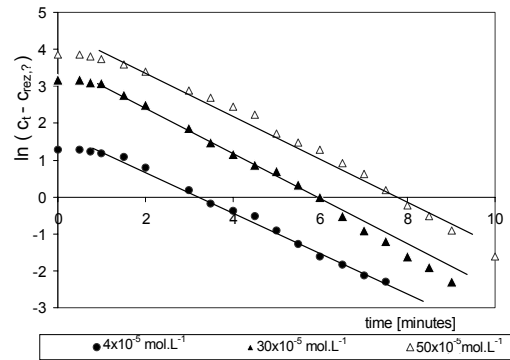


Fig. 2: First order reaction curves for the adsorption kinetic of oxine on malachite at different initial concentrations and 25°C

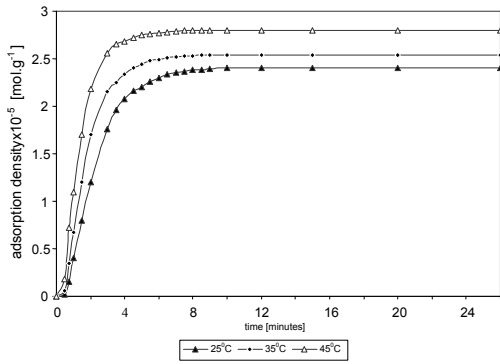


Fig. 3: Variation of oxine adsorption density on malachite as a function of time at different testing temperatures and the initial  $30 \cdot 10^{-5} \text{ mol L}^{-1}$  oxine concentration

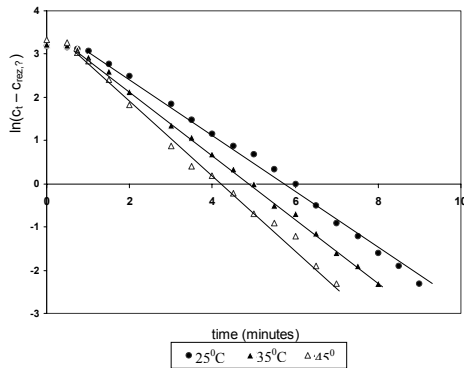


Fig. 4: Specific first order reaction curves for the adsorption kinetic of oxine on malachite at different testing temperatures and initial  $30 \cdot 10^{-5} \text{ mol L}^{-1}$  oxine concentration

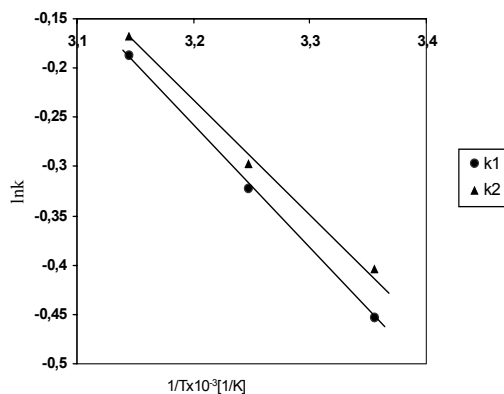


Fig. 5: Representation of the Arrhenius' equation in order to calculate the activating energy  $k_1$  - related to all the points plotted in Fig. 4,  $k_2$  - related to data obtained 1 minute after the test started

In order to find the reaction rate constant  $k$ , we used furthermore the equation (3) and we plotted  $\ln(c_t - c_{\text{rez},\infty})$  as a function of time for the studied initial oxine concentration (Fig. 4). The reaction rate constants were calculated from the straight lines slopes with statistic program. Table 4 presents the rate constants and correlation coefficients ( $R^2$ ) from the statistic data analysis of the experimental values.

Values for  $k_1$  were statistically calculated related again to all the points plotted in fig. 4, respectively for the time period from 0 to 9 minutes for  $25^\circ\text{C}$ ; 0 to 8 minutes  $35^\circ\text{C}$ ; 0 to 7 minutes for  $45^\circ\text{C}$ . The increase of the reaction rate constant with 14.04% may be noticed for each increasing interval of the temperature ( $10^\circ\text{C}$ ).

As previously described,  $k_2$  was calculated only with data obtained 1 minute after the test started and an increase with 5.17% for  $25^\circ\text{C}$ , 2.48% for  $35^\circ\text{C}$  and 2.07% for  $45^\circ\text{C}$  occurs by reporting  $k_2$  to  $k_1$ .

The activating energy for the oxine adsorption process on malachite was determined with the Arrhenius' equation:

$$k = A \cdot e^{-\frac{E_a}{RT}} \quad (4)$$

and in its logarithmic form:

$$\ln k = \ln A - \frac{E_a}{RT} \quad (5)$$

Based on the reaction rate constants  $k_1$  and  $k_2$  at all the studied temperatures (see Table 4)  $\ln k$  was illustrated graphically as a function of  $1/T$  (Fig. 5). The activating energy was calculated from the straight line slope with the statistic program. The activating energy for the oxine adsorption on malachite is  $E_a = 10.4807 \text{ kJ mol}^{-1}$  for  $k_1$  and is decreasing to  $9.2931 \text{ kJ mol}^{-1}$  for  $k_2$ .

The reactions occurring at the limit of the diffusion layer have smaller activating energies, which may also be explained by the fact that the energetic barriers that should be exceeded in case of diffusion in the bulk solution are generally small.

## CONCLUSIONS

Kinetics and equilibrium adsorption experiments were conducted in order to evaluate the adsorption characteristics of a chelating agent, namely 8-hydroxyquinoline (oxine) on malachite. Results revealed some focal points regarding the oxine adsorption on malachite, as following:

- The reaction rate constant is independent to the collector concentration; the  $k$  values are almost

the same for the different experimental concentrations;

- The effect of the temperature on the reaction rate is not very significant;
- The activating energy value for oxine adsorption on malachite suggests that the reactions should occur at the limit of the diffusion layer.

The experimental kinetic data could predict the malachite floatability; furthermore some connections shall be made between the parameters and performances during the conditioning stage in flotation and the adsorption kinetic in order to optimise the selectivity and the recovery of the desired mineral.

### REFERENCES

1. Rigbom, A., 1967. The complex in analytical chemistry, Dumond, Paris.
2. Marabini, A.M., M.Barbaro, A.Falbo, C.Cozza and S.Qaresima, 1993. Interaction mechanism of a new chelating collector and copper sulphide minerals, Proceedings, XVIII Int. Miner. Process. Congr., vol.5, pp.1375-1383
3. Nagaraj, D. R. and P. Somasundaran, 1981. Chelating reagents as collectors in flotation: oxines-cooper minerals system. *Min. Eng.*, 33: 1351-1357.
4. Bustamante, H. and H. L.Shergold, 1983. Surface Chemistry and Flotation of zinc oxide minerals: 2. Flotation with chelating reagents. *Trans. Inst.Min. Metall., Sect. C.*, 92: 208-215.
5. Oprea, G. and C.Mihali, 2001. The copper, lead and zinc recovery of the minerals partial oxidated with chelating action reagents. *Stud. Univ. Babeş Bolyai,Cluj Napoca (Romania) , Chemia*, XLVI, 1-2: 175-181.
6. Kusaka, E., K. Maegawa, Y. Fukunaka, M. Ninae and Y. Nakahiro, 1999. Two – liquid flotation of fine oxide particles with 8- hydroxychinoline. *The Canadian J. of Chem. Eng.*, 77: 62-68.
7. Oprea, G., C. Mihali, V. Danciu, M. Podariu, 2004. The study of 8-hydroxychinoline and salicylaldoxime action at the malachite flotation. *J. Min.Met.*, 40 A, 1:49-63.
8. Cecile, J. L. 1978. Chelating reagents in flotation. PhD Thesis, Univ. of Orleans: 94-136.
9. Oprea, G. and E. Chifu, 1986. Infrared spectroscopic investigation of the adsorption products of 8-hydroxychinoline on malachite. *Stud. Univ. Babeş Bolyai,Cluj Napoca (Romania) , Chemia*, XXXI, 2: 65-68.
10. Baldea, I., 2002. *Chemical Kinetics*, Cluj Napoca (Romania) University Press, pp: 102-135.