

Effects of Mixing Ratio and Size of Egg-Shell on Boiling and Compression Test of Mixed Charcoal

Bopit Bubphachot, Rujipas Seeladlao and Songchai Wiriyapumpaiwong
Faculty of Engineering, Mahasarakham University, Khamriang, Kantarawichai,
Maha Sarakham, Thailand 44150

Abstract: Problem statement: The use of waste material is one of the options to add value to the residue. Nowadays, solid fuel development is necessary in current situation due to high price fossil fuel and the reduction of resource. Wood charcoal is widely used in the country which has abundant of forest. Becoming charcoal, it needs to be burnt under optimum condition. However, from this process the loss quality as in the form of breakage charcoal which is the blackish residue consisting of impure carbon is obtained. The price and utilization of this left are less benefit. Therefore, the improvement of charcoal residue by adding egg-shell powder is of interesting. The aim of this research is to study the feasibility of production of compressed charcoal mixed with egg-shell to extend the cooking temperature and time. **Approach:** Egg-shell was ground and pass through a sieve to get the different particle sizes. Three levels of particle sizes were achieved in the range of 300-600 microns (coarse), 150-300 microns (moderate) and less than 150 microns (fine). For the charcoal, it was obtained from the brakeage charcoal and ground to powder to be substance for making compressed charcoal. The ground charcoal was mixed with egg-shell powder at different ratios of 90:10, 85:15 and 80:20 by weight. The mixture was then compressed as a cylindrical shape by charcoal wet extruder. The formed charcoal was dried by open sun drying and was tested for compressive strength and water boiling. **Results:** The results showed that egg-shell powder enhanced the thermal property of charcoal regard to the results from water boiling. **Conclusion/Recommendations:** The best results of the highest compressive strength and the average water temperature were 89 kgf and 90°C for 45 min when application of coarse powder egg-shell at mixing ratio of 85:15.

Key words: Waste material, charcoal, egg-shell, wet extruder

INTRODUCTION

In current economic circumstance, the price of petrol is higher than the past. For developing countries, charcoal and firewood play an important role in rural areas because most population has low income. However, making of charcoal and using of firewood destroy natural resource and release pollutant gases. The good quality biomass charcoal has been investigated regard to compressing process and kinds of biomass. Many kinds of biomass were used as raw materials in the charcoal production, such as rice straw (Thassawong and Unpimpa, 2002), chaff (Jattawa-Pakdee and Promwijit, 2002), corncob (Nahua-Nong and Namwongsa, 2002), cassava tree (Boonsoo and Joomba, 2003), coconut shell (Surin and Lakhongbu, 2002). Moreover, the influence of particles size biomass charcoal on the compressive strength and burning behavior was studied (Wiriyapumpaiwong *et al.*, 2004; Seker, 2004; Weert *et al.*,

2001) due to good thermal storage property. Probably, it can be extended the burning time during cooking.

To reduce the pollutant gases, the blackish residue was reused to produce solid fuel. Furthermore, the egg-shell is normally garage waste. In this study, it was chosen as mixed material with blackish residue. Therefore, the improvement of charcoal residue by adding egg-shell powder is interested. The aim of this research is to study the feasibility of production of compressed charcoal mixed with egg-shell by varying amount and partied size of egg-shell powder.

MATERIALS AND METHODS

There are 2 materials in this experiment, charcoal powder and egg-shell powder. Egg-shell was ground and pass through a sieve to get the different sizes of particle. Three levels of particle sizes were in the range of 300-600 microns (coarse), 150-300 microns

Corresponding Author: Bopit Bubphachot, Faculty of Engineering, Mahasarakham University, Khamriang, Kantarawichai, Maha Sarakham, Thailand 44150

(moderate) and less than 150 microns (fine). The standard sieve is illustrated in Fig. 1. The details of the mixed ratio are shown in Table 1.

Extrusion machine: The wet charcoal extruder is a forming machine which consists of two main part functions. The first part is the power transmission, a 3 hp gear motor and gear reducer ratio of 1:10 and second part is the charcoal extruder machine which includes screw and cylinder made of hardness SKD 11 steel with a diameter of 120 mm. Screw pitch distance is 30 mm. The mould characteristic is the hexagon shape with each size of 20 mm. The section 3 of the wet charcoal extruder is shown in Fig. 2.

Table 1: The mixed ratio of specimens

Charcoal (micron)	Size of egg-shell (micron)	Mixed ratio (%) charcoal: Egg-shell
600	< 150	90:10
	150-300	
	300-600	
600	< 150	85:15
	150-300	
	300-600	
600	< 150	80:20
	150-300	
	300-600	



Fig. 1: Standard sieve: (a) the range of 150 microns; (b) the range of 300 microns and (c) the range of 600 microns

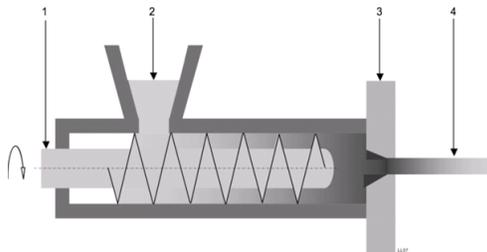


Fig. 2: Section view for the wet charcoal extruder (1) the compression screw; (2) feed hopper; (3) mould and (4) formed charcoal

Water boiling test: The formed charcoal was dried by open sun drying for one day and used to test of water boiling. The testing condition is to boil water of 0.5 L at the same weight is 0.5 kg of formed charcoal. Thermocouples (k type) which installed at three different positions as shown in Fig. 3 was use to measure water temperature and the water temperature was recorded in every 5 min.

Compression test: There are 3 samples with similar weight and smooth cross-section to be tested for the compressive strength. The testing machine is set a speed of 0.5 mm min⁻¹ and then the charcoal is put into the testing machine. The vertical axis of the sample is shown in Fig. 4. The next step is to start the machine, wait until metal plate touch to the top of the sample. The metal plate connected to load cell and set up a Linear Variable Differential Transformer (LVDT). After that, the scales of the load cell and LVDT will be adjusted to zero. Sample data was recorded in details of load and displacement in every 0.01 mm. The machine will stopped when the load is decreased to 75% of maximum load.

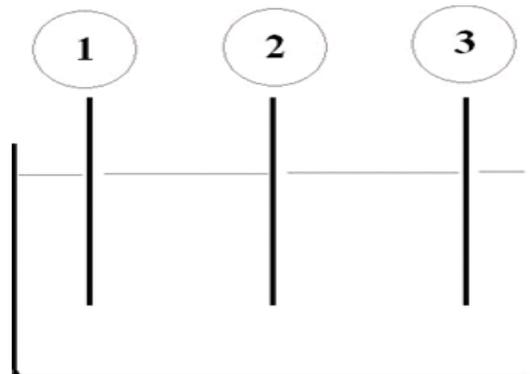


Fig. 3: Measured position of water boiling test

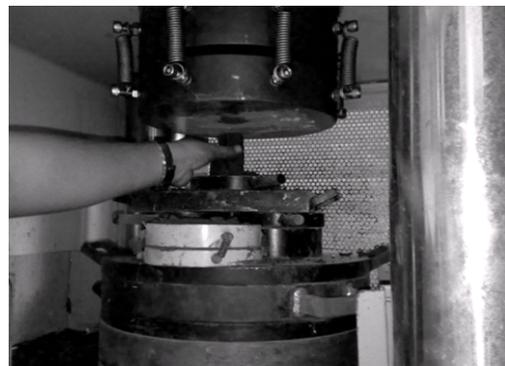


Fig. 4: Compressive strength test

RESULTS

Water boiling testing: A comparison of temperature and time of the boiling water using three different sizes of egg-shell powder shows that a charcoal without egg-shell powder provided the maximum average temperature. The next are charcoal mixed with egg-shell powder's sizes of 300-600 micron, 150-300 micron and less than 150 micron respectively in Fig. 5.

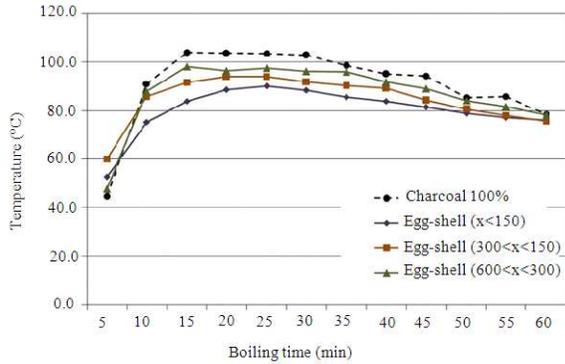


Fig. 5: A comparison of temperature and time of the boiling water using charcoal mixed with egg-shell powder in the ratio of 90:10

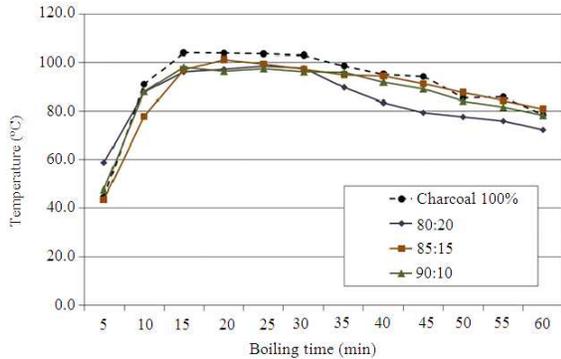


Fig. 6: A comparison of temperature and time of a boiling water using charcoal mixed with egg-shell powder's size of 300-600 micron in different ratio

Table 2: The compressive strength of specimens

Particle size of charcoal (micron)	Size of egg-shell (micron)	Mixed ratio (%) charcoal: Egg-shell	Compressive strength (kg _f)
600	<150		88.80
	150-300	90:10	71.10
	300-600		70.33
600	<150		124.30
	150-300	85:15	99.40
	300-600		89.10
	<150		96.50
	150-300	80:20	88.70
	300-600		71.03

Figure 6 shows a comparison of temperature and time of a boiling water using charcoal mixed with egg-shell powder's size of 300-600 micron in different ratio. The highest average temperature was obtained at the ratio of 85:15.

Compressive strength testing: From the experiment, Table 2 shows the compressive strength of specimens. An average compressive strength of charcoal mixed with egg-shell powder's size of less than 150 micron was higher than sizes of 150-300 and 300-600 micron respectively.

DISCUSSION

Water boiling testing: A condition of the experiment was to boil water with an equal weight of the charcoal, the amount of the charcoal in the test was reduced when the ratio of egg-shell powder were increased. However, the difference of the average temperature between the charcoal mixed with egg-shell powder and normal charcoal in every condition was similar. The temperature was increased in the initial step and slightly decreased until the final step as illustrate.

Moreover, the amount of egg-shell powder was higher than other ratios thus, burning this mixed charcoal rapidly produced ash and the temperature was visibly reduced more than others.

Compressive strength testing: A smaller size of egg-shell powder can fill gaps in the charcoal better than a bigger size, the smaller size can stand for a high compressive strength.

CONCLUSION

The ground charcoal was mixed with egg-shell powder at different ratios of 90:10, 85:15 and 80:20 by weight. The mixture was then compressed as a cylindrical shape by charcoal wet extruder. The formed charcoal was dried by open sun drying and was tested for compressive strength and water boiling. The results showed that egg-shell powder enhanced the thermal property of charcoal regard to the results from water boiling. The best results of the highest compressive strength and the average water temperature were 99.4 kg_f and 90°C for 45 min when application of coarse powder egg-shell at mixing ratio of 85:15.

ACKNOWLEDGMENT

The researcher would like to express the appreciation to the Faculty of Engineering,

Maharakham University, Maharakham Thailand for the financial support.

REFERENCES

- Boonsoo, R. and O. Joompa, 2003. Production of Charcoal from cassava tree. B.S. Thesis, Maharakham University, Maharakham, Thailand.
- Jattawa-Pakdee, N. and S. Promwjit, 2002. Production of charcoal from husk. B.S. Thesis, Maharakham University, Maharakham Thailand.
- Nahua-Nong, T. and H. Namwongsa, 2002. Production of charcoal from cob. B.S. Thesis, Maharakham University, Maharakham, Thailand.
- Seker, M., 2004. Distribution of the residence time in a single-screw extruder with differing numbers of mixing elements. *Int. J. Food Sci. Technol.*, 39: 1053-1060. DOI: 10.1111/j.1365-2621.2004.00888.x
- Surin, W. and W. Lankongbu, 2002. Production of charcoal from coconut shell. B.S. Thesis, Maharakham University, Maharakham, Thailand.
- Thassawong, J. and W. Unpimpa, 2002. Production of charcoal from straw. B.S. Thesis, Maharakham University, Maharakham Thailand.
- Wiriyumpaiwong, S., C. Tumngam and S. Kodsunghan, 2004. Influence of particle size of biomass coal on combustion. *KKU Eng. J.*, 32: 61-75. <http://www.en.kku.ac.th/enjournal/index.php?option=content&task=view&id=190>
- Weert, X., C.J. Lawrence, M.J. Adams and B.J. Briscoe, 2001. Screw extrusion of food powder: Prediction and performance. *Chem. Eng. Sci.*, 56: 1933-1949. DOI: 10.1016/S0009-2509(00)00463-2